



**HAL**  
open science

## Manufacturing of biocomposite foams PLA / Natural fibres

Jorge Chaires Vasquez, Nicolas Le Moigne, Martial Sauceau, Jacques Fages

► **To cite this version:**

Jorge Chaires Vasquez, Nicolas Le Moigne, Martial Sauceau, Jacques Fages. Manufacturing of biocomposite foams PLA / Natural fibres. EMSF 2019 - 17th European Meeting on Supercritical Fluids, 7th European Meeting on High Pressure Technology, Apr 2019, Ciudad Real, Spain. . hal-02510049

**HAL Id: hal-02510049**

**<https://imt-mines-ales.hal.science/hal-02510049v1>**

Submitted on 24 Mar 2020

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



# Manufacturing of biocomposite foams PLA / Natural fibres


Jorge Chaires Vasquez<sup>a,b</sup>, Nicolas Le Moigne<sup>a</sup>, Martial Sauceau<sup>b</sup>,  
Jacques Fages<sup>b</sup>

<sup>a</sup> C2MA, IMT Mines Al s, Universit  de Montpellier, 30319 Al s, France


<sup>b</sup> Centre RAPSODEE, IMT Mines Albi, CNRS, Universit  de Toulouse, 81013 Albi, France

## INTRODUCTION AND OBJECTIVE

- ◆ Foaming is very common process used with polymers to lighten the materials while keeping acceptable mechanical properties.
- ◆ Bio-polymer foams are a viable alternative to petrochemical plastics.
- ◆ A polymer foaming process using supercritical CO<sub>2</sub> has been developed and applied to thermoplastics [1]. It is implemented via an extrusion process, CO<sub>2</sub> being injected in the barrel of an extruder where it acts as a removable plasticizer before giving its foaming effect through the die exit. It has been successfully applied to biopolymers like PLA (poly-lactic acid) [2] and some nanobiocomposites [3].
- ◆ Foaming of PLA reinforced with natural fibres: flour of spruce wood, cellulosic fibres (Arbocel) and flax fibres. The use of PLAs with different properties allows a better understanding of the process.

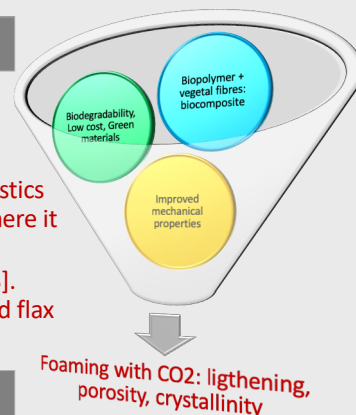


## MATERIALS AND METHODS

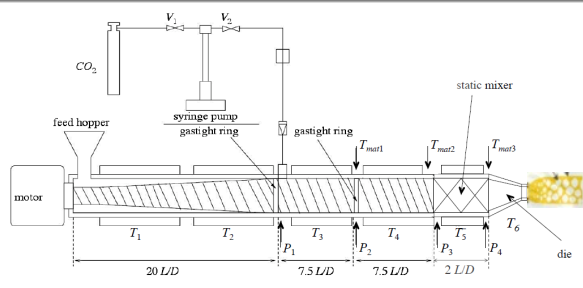

**Polymers used:**  
Poly-(lactic acid) : injection & extrusion grade

**Fibres used:**

- ◆ Wood flour
- ◆ Cellulose fibres
- ◆ Flax fibres



**Extrusion assisted with supercritical CO<sub>2</sub>:**  
Used as a plasticizer inside the extruder and as a physical blowing agent through the die to foam the PLA

**PLA foam characterization:**

- ◆ scanning electron microscopy (SEM)
- ◆ water pycnometry

## RESULTS AND DISCUSSION

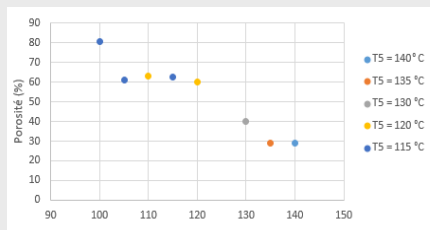


Figure 1. Porosity as a function of die temperature T<sub>6</sub> for different pre-expansion temperature T<sub>s</sub> for PLA mixture extrusion-foaming

With the injection-grade PLA, the process is difficult to control due to the recrystallization of the PLA before the die exit. At low temperature, a heterogeneous foamy structure (porosity >80 %) was obtained. The crystallisation behaviour seems to be the major factor influencing the structure of produced foams. High crystallinity favours the longitudinal expansion rather than the radial expansion of the foam. For the foaming of mixture of both PLA grades (Figure 1), similar morphology but higher porosity was achieved with however less pronounced layered structures at the surface of the extrudate.

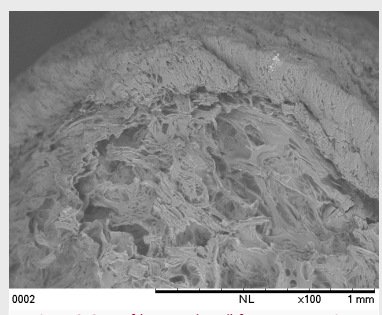


Figure 2. SEM of (PLA + Arbocel) foam cross section exhibiting outer skin and layered structure.

When incorporating natural fibres, foams with a porosity up to 80 % could be obtained for the composites with 5 % of the fibres with the smallest dimensions (cellulose and wood flour). However, a skin effect was observed (figure 2). The outer layer of the extrudates exhibited almost no porosity, resulting in a smoother sample surface and a very stable process. In the core of the samples, the foaming remains irregular and several ruptures were observed due to limited interfacial adhesion between the fibres and the PLA matrix. The optimal foaming temperatures are decreased by the presence of the fibres. The foaming process is also impeded by too high fibre size and shape factor. Indeed, for the longer and bigger fibres (wood and flax), porosity below 30 % was obtained and the process stopped due to the extruder obstruction.

## CONCLUSION AND PERSPECTIVES

While pure PLA foaming is a well-mastered process, incorporating natural fibres though promising to control foam structure and physical properties, appears much more difficult. To get polymer biocomposite foams with improved mechanical and end-user properties, process optimization is now required.

## REFERENCES

1. C Nikitine, E Rodier, M Sauceau, J-J Letourneau, J Fages, Controlling the structure of a porous polymer by coupling supercritical CO<sub>2</sub> and single screw extrusion process *J. Appl. Polym. Sci.* **2010**, *115*, 981-990.
2. M Chauvet, M Sauceau, J Fages, Extrusion assisted by supercritical CO<sub>2</sub>: A review on its application to biopolymers. *J. Supercrit. Fluids* **2017**, *120*(2), 408-420.
3. N Le Moigne, M Sauceau, M Chauvet, J-C B n zet, J Fages, Microcellular Foaming of (Nano) Biocomposites by Continuous Extrusion Assisted by Supercritical CO<sub>2</sub>. *In: Biomass Extrusion and Reaction Technologies: Principles to Practices and Future Potential. ACS, Chapter 9*, **2018**, 171-188.